

Physical and optical properties of Dy³⁺ bismuth barium borate glasses

Rungsan Ruamnikhom^{1,*}, Patarawagee Yasaka² and Jakrapong Kaewkhao²

¹Faculty of Liberal Arts, Rajamangala University of Technology Rattanakosin,
Nakhon Pathom 73170, Thailand

²Center of Excellence in Glass Technology and Materials Science (CEGM),
Nakhon Pathom Rajabhat University, Nakhon Pathom 73000, Thailand

Abstract

Trivalent dysprosium (Dy³⁺) doped bismuth barium borate glasses with composition (40-x) B₂O₃:40Bi₂O₃:20BaO:xDy₂O₃ (where x = 0, 0.50, 1.00, 1.50, 2.00 and 2.50 mol.%) were prepared by melt quench technique at 1,100 °C. The density of the prepared samples was measured using Archimedes' principle. The results show the increasing in the glass density with respect to increasing in the doping concentrations of Dy₂O₃. The molar volume of the bismuth barium borate glasses doped with Dy³⁺ were calculated and found to be in the range 30.63-30.95 cm³/mol. The analysis of FTIR spectrum of the sample depicts that the glass network is built up of mainly BiO₃, BO₃ and BO₄ units. The UV visible absorption spectra of the dysprosium doped bismuth barium borate glasses were found to be consists of five absorption peaks which correspond to transitions from ground state ⁶H_{15/2} to various excited states.

Keywords: trivalent dysprosium, bismuth barium borate, optical

Article history: Received 27 February 2017, Accepted 17 September 2017

1. Introduction

In recent years, a special attention is intensively focused on the rare earth (RE) ions doped glasses on the fabrication of new generation solid state devices like white LEDs, solid state lasers, flat panel displays, planar waveguide, optoelectronic devices and broadband amplifiers etc., due to their inhomogeneous line widths, flexibility in the selection of wide range of chemical composition and mass production [1, 2]. Among the various glasses, borate glasses are excellent host matrices because boron trioxide (B₂O₃) acts as a good glass former and flux material [3]. Borate glasses are structurally more intricate compared to phosphate or silicate glasses due to two types of coordination of boron atoms with 3 and 4 oxygens and the structure of vitreous B₂O₃ consists of a random network of boroxyl rings and BO₃ triangles connected by B-O-B linkages. Moreover, the addition of a modifier oxide causes a progressive change of some BO₃ triangles to BO₄ tetrahedra and results in the formation of various cyclic units like diborate, triborate, tetraborate or pentaborate groups [4].

The heavy metal ions like Bi₂O₃, PbO, PbF₃, etc., containing in borate glasses, decreases the host phonon energy and thereby improves the effective fluorescence [5]. Moreover, the bismuth oxide contained host glass matrix improves chemical durability of the glass [6]. Despite, the Bi₂O₃ is not a classical network former; it exhibits some superior physical properties like high density, high refractive index and exhibits high optical

basicity, large polarizability and large nonlinear optical susceptibility [7]. The presence of two network forming oxides such as classical B₂O₃ and the conditional Bi₂O₃ glass former, the possible participation in the glass structure of both boron and bismuth ions with more than one stable coordination, the capability of the bismuth polyhedral and of the borate structural groups to form independent interconnected networks [8].

Over the last several years, bismuth barium borate glasses are also useful for variety of optical applications such as radiation shielding window, gamma-rays shielding materials and scintillation counters [9, 10]. Among the various rare earth ions, Dy³⁺ ions is one of the good luminescent ion which emits blue and yellow and moderate red emission. Despite, possible visible emission is exhibited from the Dy³⁺ ions, a special attention has also been focused on Dy³⁺ doped complexed materials due its capability of white light emission under the ultraviolet or blue excitation wavelengths [11]. Moreover, Dy³⁺ doped glasses are also used as promising materials for telecommunication technological applications due to their infrared emission at 1.32 μm apart from the display device applications [12].

The purpose of this study was therefore to develop bismuth barium borate glasses doped with Dy³⁺ ions. The study also focused on the fabrication process, material characterizations and analyses. The physical,

*Corresponding author; e-mail: rungsan.rua@rmutr.ac.th

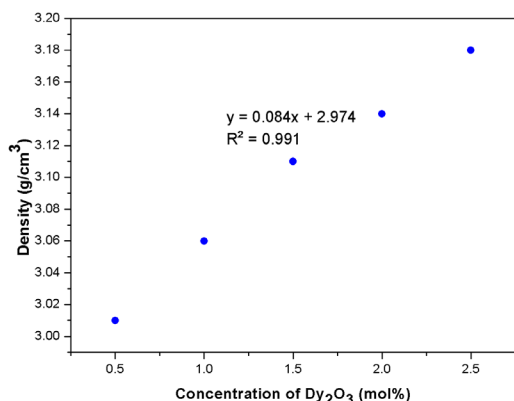


Figure 1 Densities of the Dy³⁺-doped bismuth barium borate glasses with respect to the Dy₂O₃ content

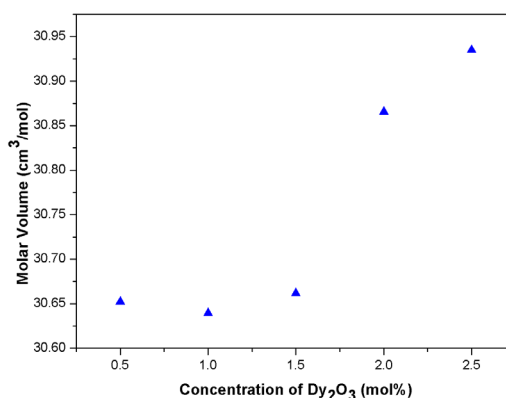


Figure 2 Molar volumes of the Dy³⁺-doped bismuth barium borate glasses with respect to the Dy₂O₃ content

structural and optical properties were investigated with respect to the concentrations of the Dy³⁺ ions.

2. Materials and methods

Dy₂O₃ doped bismuth barium borate glasses with compositions (40-x) B₂O₃:40Bi₂O₃:20BaO:xDy₂O₃ (where x having values 0.5, 1.0, 1.5, 2.0 and 2.5 mol.% resp.) have been melted in alumina crucible by melt-quench technique at 1,100 °C for 3 hours. The melts were air quenched by pouring it onto a preheated stainless steel mould and annealed at 500 °C for 3 hours to decreased thermal strains. The cut glass samples were polished into dimension 1.00 cm × 1.50 cm × 0.30 cm for the study of physical and optical properties. The densities based on Archimedes' principle using water at the room temperature. The molar volume was calculated using the relation $V_M = M_T/\rho$, where M_T is the total molecular weight of the multicomponent glass system. The optical absorption spectra of the glass samples were recorded using a Shimadzu 3600 UV-VIS-NIR spectrophotometer in the range 200-2,500 nm. The FTIR vibration spectra of the present glasses were recorded at room temperature in the wavenumber range 650-3,000 cm⁻¹ using an Agilent-Cary 630 FTIR which has a resolution of 1 cm⁻¹.

3. Results and discussion

The density of the prepared samples based on the Archimedes' principle, the determined density of the glass samples varied in a range of 3.01-3.18 g/cm³ with respect to the Dy₂O₃ concentrations are shown in Figure 1. The results show the increase in the glass density with respect to increase in the doping concentrations of Dy₂O₃. The glass density was also increased because of relatively higher molecular mass of Dy₂O₃ in comparison to that of B₂O₃ within the glass matrix. In addition, the percentage of the Dy₂O₃ content also performed differently within the matrix. The molar volume is almost stable from 0.50 to 1.50

% mol concentrations, due to Dy³⁺ acting as a part of former, and increased when the concentrations are in range of 1.50%-2.50%, due to Dy³⁺ entering into the glass network as a modifier and non-bridging oxygen (NBOs), as shown in Figure 2.

The absorption spectra of the Dy³⁺ doped bismuth barium borate glasses recorded in the UV-Vis-NIR region are shown in Figure 3. It is observed from the figure that, the absorption spectra exhibit five absorption bands around 796, 902, 1096, 1276 and 1681 nm due to the 4f⁹ electronic transition of the Dy³⁺ ions from the ⁶H_{15/2} ground level to the various excited states such as ⁶F_{5/2}, ⁶F_{7/2}, ⁶F_{9/2}, ⁶H_{7/2}, ⁶F_{11/2}, ⁶H_{9/2} and ⁶H_{11/2}, respectively [13]. As the concentration increases, the intensity of the absorption bands is found to increase whereas the band center does not differ. The absorption transitions such as ⁶H_{15/2} → ⁶F_{11/2} and ⁶H_{15/2} → ⁶H_{11/2} are found to possess higher intensity which are highly sensitive to the host environment known as hypersensitive transitions [14].

Figure 4 shows the FTIR spectra of (40-x)B₂O₃:40Bi₂O₃:20BaO:xDy₂O₃ with x = 0.0, 0.5, 1.0, 1.5, 2.0 and 2.5 mol%, respectively. According to Krogh-Moe model, the structure of borate glass consists of BO₃ triangles with certain fraction of six membered (boroxol) rings [15]. In B₂O₃ glasses boron [B³⁺] ions are triangularly coordinated by oxygen to form glasses easily. The BO₃ triangles are corner bonded in a random network [16]. The introduction of transition metal ions in these glasses helps the boron to form tetraborate groups and progressive substitution of boroxal rings by triborate and tetraborate groups [17]. The boroxal ring shows its characteristic frequency at 806 cm⁻¹ and the presence or absence of this band decides the existence or absence of boroxal rings in the structure. In the present set of glasses no band was observed at or around 806 cm⁻¹ indicating that no boroxal rings are present in these glasses. The peaks of the IR spectra of the glasses under study are listed

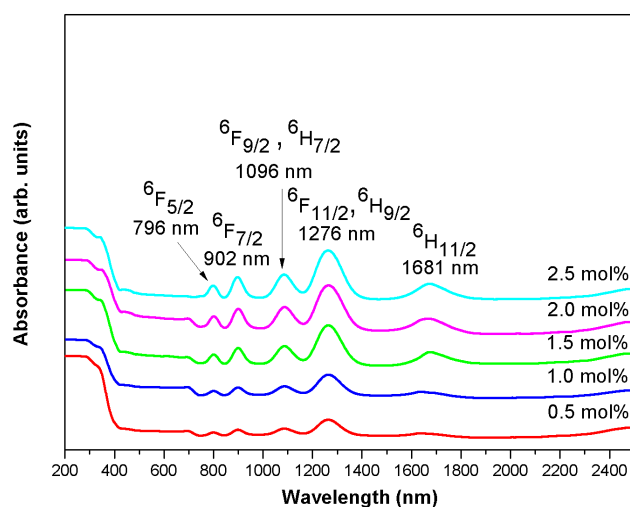


Figure 3 Absorption spectra of the Dy³⁺-doped bismuth barium borate glasses with respect to the Dy₂O₃ content

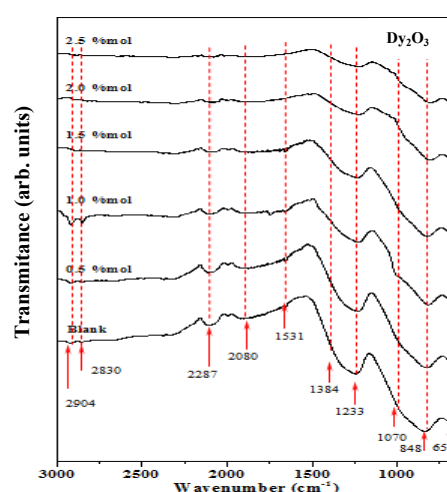


Figure 4 Infrared spectra of the Dy³⁺-doped bismuth barium borate glasses with respect to the Dy₂O₃ content

Table 1 Peak table of FTIR analysis of Dy³⁺-doped bismuth barium borate glasses with respect to the Dy₂O₃ content

Wavenumber (cm ⁻¹)	IR band assignments
651	The bending vibrations of B-O-B linkages of BO ₃ units
848	Symmetrical stretching vibration of the Bi-O bonds in the BiO ₃ groups
1070	Stretching vibrations of B-O bonds in BO ₄ units from tri, tetra and penta borate groups
1233	B-O _{sym} stretch in BO ₃ units from pyro and ortho borate groups
1384	B-O _{sym} stretch in BO ₃ units from varied types of borate groups
1531	B-O ⁻ stretch in BO ₂ O ⁻ units from varied types of borate groups
2080 - 2904	OH bending mode of vibration

in Table 1. The bands observed in the region 2080-2940 in all the glass samples are attributed to the hydroxyl or water group [18]. The present set of glasses show transmission bands in regions 2904, 2830, 2287, 2080, 1531, 1384, 1233, 1070, 848 and 651 cm⁻¹. It has been reported that the bands observed in the region 1233 cm⁻¹ are due to the asymmetrical stretching relaxation of the B-O bond of trigonal BO₃ units [19]. The band around 1070 cm⁻¹ originates from B-O bond stretching of the tetrahedral BO₄ units and is due to the vibration of some boron atoms attached to the non-bridging oxygen in the form of BO₄ vibrations [20]. The shoulder around 848 cm⁻¹ is related to the symmetrical stretching vibration of Bi-O in [BiO₃] group [21]. The band observed around 651 cm⁻¹ is the bond bending mode of B-O-B vibrations [22, 23].

4. Conclusions

Dy³⁺-doped bismuth barium borate glasses with composition (40-x)B₂O₃:40Bi₂O₃:20BaO:xDy₂O₃ (where x = 0, 0.50, 1.00, 1.50, 2.00 and 2.50 mol.%) were prepared by melt quenching technique at 1,100 °C.

The density of the prepared samples was measured using Archimedes' principle. The results show the increasing in the glass density with respect to increasing in the doping concentrations of Dy₂O₃. The molar volume of the bismuth barium borate glasses doped with Dy³⁺ were calculated and found to be in the range of 30.63-30.95 cm³/mol. The analysis of FTIR spectrum of the sample depicts that the glass network is built up of mainly BiO₃, BO₃ and BO₄ units. The UV visible absorption spectra of the Dysprosium doped bismuth barium borate glasses were found to be consists of five absorption bands around 796, 902, 1096, 1276 and 1681 nm due to the 4f⁹ electronic transition of the Dy³⁺ ions from the ⁶H_{15/2} ground level to the various excited states such as ⁶F_{5/2}, ⁶F_{7/2}, ⁶F_{9/2}, ⁶H_{7/2}, ⁶F_{11/2}, ⁶H_{9/2} and ⁶H_{11/2}, respectively.

Acknowledgements

The authors would like to thanks Rajamangala University of Technology Rattanakosin (RMUTR) for financial support for this research. Also, we would like to thanks Center of Excellence in Glass Technology

and Materials Science (CEGM), Nakhon Pathom Rajabhat University for supporting the technique of glass preparation and instruments.

References

- [1] Praveena R, Vijaya R, Jayasankar CK. **Spectrochim. Acta Part A**. 2008; **70**: 577-586.
- [2] Rajesh D, Balakrishna A, Ratnakaram YC. Luminescence, structural and dielectric properties of Sm^{3+} impurities in strontium lithium bismuth borate glasses. **Opt. Mat.** 2012; **35**: 108-116.
- [3] Subhadra M, Kistaiah P. Infrared and raman spectroscopic studies of alkali bismuth borate glasses: Evidence of mixed alkali effect. **Vibrational Spectroscopy**. 2012; **62**: 23-27.
- [4] Ramteke DD, Annapurna K, Deshpande VK, Gedam RS. Effect of Nd^{3+} on spectroscopic properties of lithium borate glasses. **J. Rare Earths**. 2014; **32** (12): 1148-1153.
- [5] Srivastava P, Rai SB, Rai DK. Optical properties of Dy^{3+} doped calibo glass on addition of lead oxide. **Spectrochim. Acta A**. 2003; **59**: 3303-3311.
- [6] Doualan JL, Girard S, Haquin H, Adam JL, Montagne J. Spectroscopic properties and laser emission of Tm doped ZBLAN glass at 1.8 μm . **Opt. Mat.** 2003; **24**: 563-577.
- [7] Singh SP, Chakradhar RPS, Rao JL, Karmakar B. Optical absorption and photoluminescence properties of MnO_2 doped $23\text{B}_2\text{O}_3\text{-}5\text{ZnO-}72\text{Bi}_2\text{O}_3$ glasses. **Phys B**. 2010; **405**: 2157-2161.
- [8] Pascuta P, Borodi G, Culea E. Influence of europium ions on structure and crystallization properties of bismuth borate glasses and glass ceramics. **J. Non-Cryst. Solids**. 2008; **354**: 5475-5479.
- [9] Kaewkhao J, Pokaipisit A, Limsuwan P. Study on borate glass system containing with Bi_2O_3 and BaO for gamma-rays shielding materials: Comparison with PbO. **Journal of Nuclear Materials**. 2010; **399**: 38-40.
- [10] Boonin K, Kaewkhao J, Limsuwan P. Preparation and properties of $\text{Bi}_2\text{O}_3\text{-B}_2\text{O}_3\text{-Nd}_2\text{O}_3$ glass system. **Advanced Materials Research**. 2010; **93**: 336.
- [11] Zhongfei M, Yihua H, Li C, Xiaojuan W. Enhanced luminescence of Dy^{3+} in $\text{Y}_3\text{Al}_5\text{O}_{12}$ by Bi^{3+} co-doping. **J. Lumin.** 2011; **131**: 1687-1691.
- [12] Duan Z, Zhang J, Hu L. Spectroscopic properties and Judd-Ofelt theory analysis of Dy^{3+} doped oxyfluoride silicate glass. **J. Appl. Phys.** 2007; **101**: 043110-043116.
- [13] Carnall WT, Fields PR, Rajnak K. **J. Chem. Phys.** 1968; **49**: 4424-4442.
- [14] Rajesh D, Ratnakaram YC, Seshadri M, Balakrishna A, SatyaKrishna T. **Lumin J**. 2012; **132**: 841-849.
- [15] Krogh M. Interpretation of the Infrared Spectra of Boron Oxide and Alkali Borate Glasses. **Physics and Chemistry of Glasses**. 1965; **6** (46): 46-54.
- [16] Yawale SS, Yawale SP, Adgaonkar CS. Infrared Investigation of Some Borate Glasses. **Indian J. Eng. Mater. S**. 2000; **7**: 150-153.
- [17] Baia L, Stefan R, Kiefer W, Simon S. Structural of Characteristics of $\text{B}_2\text{O}_3\text{-Bi}_2\text{O}_3$ Glasses with High Transition Metal Oxide Content. **Journal of Raman Spectroscopy**. 2005; **36** (3): 262-266.
- [18] Scholzelt H. **Glass nature structure and properties**. New York: Springer Verlag; 1991.
- [19] Varsamis CP, Kamitsos EI, Chryssikos GD. Structure of Fast-Ion-Conducting AgI-Doped Borate Glasses in Bulk and Thin Film. **Physics Review B**. 1999; **60** (3885): 12-16.
- [20] Ito Y, Miyauchi K. Ionic Conductivity of $\text{Li}_2\text{OB}_2\text{O}_3$ Thin Films. **J. Non-Cryst. Solids**. 1983; **57** (3): 389-400.
- [21] Saritha D, Markandey Y, Salagram M, Vithal M, Singh AK, Bhikshamaiah G. Effect of Bi_2O_3 on Physical, Optical and Structural Studies of $\text{ZnO-Bi}_2\text{O}_3\text{-B}_2\text{O}_3$ Glasses. **J. Non-Cryst. Solids**. 2008; **354**: 5573-5579.
- [22] Roshan L, Sharma ND. Infrared Spectroscopic Study of Zinc Doped Iron Borate Glasses. **Indian Journal of Pure and Applied Physics**. 2005; **43** (828): 828-831.
- [23] Chakrabortya1 IN, Condrate RA. Characterization of Glasses. **MRS Proceedings**. 1985; **19**: 1-29.